


**STUDY ON THE
EFFECT OF AGRICULTURAL SOLID WASTE
BAGASSE ASH ON THE PROPERTIES OF
EXPANSIVE SOIL**

HRUSHIKESH RAYMOHAPATRA

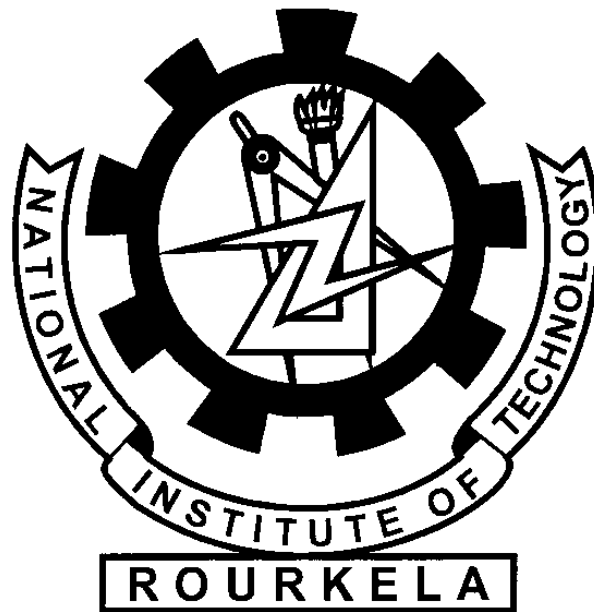

**DEPARTMENT OF CIVIL ENGINEERING
NATIONAL INSTITUTE OF TECHNOLOGY
ROURKELA-769008**

**STUDY ON THE
EFFECT OF AGRICULTURAL SOLID WASTE
BAGASSE ASH ON THE PROPERTIES OF
EXPANSIVE SOIL**

A thesis submitted in partial fulfilment of requirements

for the degree of

BACHELOR OF TECHNOLOGY

In

CIVIL ENGINEERING

By

Hrushikesh RayMohapatra

Roll no.-111CE0376

Under the Supervision of

Prof. (Dr.) N. ROY



CERTIFICATE

This is to certify that the project entitled “**Study on the Effect of Agricultural Solid Waste Bagasse Ash on the Properties of Expansive Soil**” submitted by *Hrushikesh RayMohapatra* in partial fulfillment of the requirements for the award of **Bachelor of Technology** Degree in **Civil Engineering** at National Institute of Technology, Rourkela is an authentic work carried out by him under my personal guidance and supervision. To the best of my knowledge the matter embodied in this project review report has not been submitted in any college/institute for award of any degree or diploma.

Date: 11-05-2015

Place: Rourkela

Prof. N. Roy

Professor

Department of Civil Engineering

National Institute of Technology Rourkela

NATIONAL INSTITUTE OF TECHNOLOGY ROURKELA
– 769008

ACKNOWLEDGEMENT

I am deeply thankful to the Lord Almighty for everything he has given me. I am grateful to NIT Rourkela for giving me the exposure and the resources to work on the project.

I would like to express my deepest sense of gratitude to my guide **PROF. (DR.) N.ROY** for his guidance and immense help and support during the period of the project work despite his busy schedule. It was a privilege to work under such an erudite professor.

I would like to thank **PROF. S.K. DAS, PROF. S.P. SINGH**, and all the faculties of Civil Engineering Department for their immense support during the project work.

I would love to express my deepest sense of gratitude to **PROF. S.K. SAHU**, Head, Department of Civil Engineering, who has always motivated and supported me throughout the project work.

Last but not the least; I would like to thank all the staff members of Department of Civil Engineering, especially of the Geotechnical Engineering Laboratory and all my friends and elders who have helped me throughout the process.

HRUSHIKESH RAYMOHAPATRA

111CE0376

ABSTRACT

Expansive soils swell under the influence of water and shrink when they become dry, and hence cause various problems and may also lead to failure of the structures built upon them. So, it is the duty of an engineer to evaluate and possibly modify the properties of the expansive soil before constructing any structure over the same. In this study, the industrial solid waste, Bagasse Ash, is used as an admixture to mix with the expansive soil. Bagasse Ash is generally deposited in an unscientific and random manner and causes reduction of valuable space and also leads to various geo-environmental problems. In this study an attempt is made to utilise the waste Bagasse Ash. After mixing the Virgin Expansive Soil with the Bagasse Ash, the soil properties are studied and the changes in the properties of the soil are evaluated at different percentages of Bagasse Ash. An effort is made to improve the strength of the expansive soil and reduce the plasticity index of the soil.

CONTENTS

CERTIFICATE.....	3
ACKNOWLEDGEMENT	4
ABSTRACT	5
LIST OF FIGURES	9
LIST OF TABLES	9
LIST OF SYMBOLS	10
CHAPTER 1 INTRODUCTION.....	11
1.1 General.....	11
1.2 Expansive Soil	11
1.3 Bagasse Ash.....	12
CHAPTER 2 LITERATURE REVIEW	13
2.1 Previous Works.....	13
2.2 Properties of Soil.....	14
2.2.1 Specific Gravity	14
2.2.2 Particle Size Distribution.....	14
2.2.3 Atterberg Limits.....	15
2.2.4 Free Swell Index	15
2.2.5 Unconfined Compression Test (UCS Test)	16
CHAPTER 3 EXPERIMENTAL INVESTIGATIONS.....	17
3.1 Scope of work	17
3.2 Materials	18
3.3 Preparation of samples	18
CHAPTER 4 RESULTS	21
4.1 Virgin Expansive Soil	21

4.1.1	Specific Gravity	21
4.1.2	Free Swelling Index	21
4.1.3	Grain size distribution.....	21
4.1.4	Liquid Limit.....	23
4.1.5	Plastic Limit.....	23
4.1.6	Shrinkage Limit	23
4.1.7	Standard Proctor Compaction Test.....	23
4.1.8	Unconfined Compressive Strength Test	24
4.2	Virgin Expansive Soil + 4% Bagasse Ash.....	24
4.2.1	Free Swelling Index	24
4.2.2	Liquid Limit.....	24
4.2.3	Plastic Limit.....	24
4.2.4	Shrinkage Limit	24
4.2.5	Standard Proctor Compaction Test.....	24
4.2.6	Unconfined Compressive Strength Test	24
4.3	Virgin Expansive Soil + 8% Bagasse Ash.....	25
4.3.1	Free Swelling Index	25
4.3.2	Liquid Limit.....	25
4.3.3	Plastic Limit.....	25
4.3.4	Shrinkage Limit	25
4.3.5	Standard Proctor Compaction Test.....	25
4.3.6	Unconfined Compressive Strength Test	25
4.4	Virgin Expansive Soil + 12% Bagasse Ash.....	26
4.4.1	Free Swelling Index	26
4.4.2	Liquid Limit.....	26
4.4.3	Plastic Limit.....	26
4.4.4	Shrinkage Limit	26
4.4.5	Standard Proctor Compaction Test.....	26
4.4.6	Unconfined Compressive Strength Test	26

4.5	Virgin Expansive Soil + 16% Bagasse Ash.....	27
4.5.1	Free Swelling Index	27
4.5.2	Liquid Limit.....	27
4.5.3	Plastic Limit.....	27
4.5.4	Shrinkage Limit	27
4.5.5	Standard Proctor Compaction Test.....	27
4.5.6	Unconfined Compressive Strength Test	27
CHAPTER 5	COMPARISON AND DISCUSSION.....	28
5.1	Comparison	28
5.1.1	Comparison of Liquid Limit Values.....	28
5.1.2	Comparison of Plastic Limit Values	29
5.1.3	Comparison of Shrinkage Limit Values	30
5.1.4	Comparison of Plastic and Liquid Limit Values	32
5.1.5	Comparison of Plasticity Index Values	33
5.1.6	Comparison of Free Swell Index	34
5.1.7	Comparison of Maximum Dry Density (MDD) Values	35
5.1.8	Comparison of Maximum Bulk Density (MBD) Values.....	36
5.1.9	Comparison of Optimum Moisture Content (OMC) Values	38
5.1.10	Comparison of 7 Day UCS Values.....	39
5.2	Discussion	40
CHAPTER 6	CONCLUSION	42
REFERENCES		43

LIST OF FIGURES

FIGURE 1	SAMPLE OF THE EXPANSIVE SOIL.....	19
FIGURE 2	SAMPLE OF THE BAGASSE ASH.....	20
FIGURE 3	GRAIN SIZE DISTRIBUTION CURVE.....	22
FIGURE 4	EFFECT OF BAGASSE ASH ON LIQUID LIMIT VALUE.....	29
FIGURE 5	EFFECT OF BAGASSE ASH ON PLASTIC LIMIT VALUE	30
FIGURE 6	EFFECT OF BAGASSE ASH ON SHRINKAGE LIMIT VALUE	31
FIGURE 7	COMPARISON OF LIQUID LIMIT AND PLASTIC LIMIT	33
FIGURE 8	EFFECT OF BAGASSE ASH ON PLASTICITY INDEX VALUE	34
FIGURE 9	EFFECT OF BAGASSE ASH ON FREE SWELL INDEX.....	35
FIGURE 10	EFFECT OF BAGASSE ASH ON MAXIMUM DRY DENSITY VALUE	36
FIGURE 11	EFFECT OF BAGASSE ASH ON MAXIMUM BULK DENSITY VALUE.....	37
FIGURE 12	EFFECT OF BAGASSE ASH ON OPTIMUM MOISTURE CONTENT VALUE.....	39
FIGURE 13	EFFECT OF BAGASSE ASH ON 7 DAY UCS VALUE	40

LIST OF TABLES

TABLE 1	EFFECT OF BAGASSE ASH ON LIQUID LIMIT VALUE.....	28
TABLE 2	EFFECT OF BAGASSE ASH ON PLASTIC LIMIT VALUE	29
TABLE 3	EFFECT OF BAGASSE ASH ON SHRINKAGE LIMIT VALUE	31
TABLE 4	COMPARISON OF LIQUID LIMIT AND PLASTIC LIMIT	32
TABLE 5	EFFECT OF BAGASSE ASH ON PLASTICITY INDEX.....	33
TABLE 6	EFFECT OF BAGASSE ASH ON THE FSI VALUE	34
TABLE 7	EFFECT OF BAGASSE ASH ON MDD.....	35
TABLE 8	EFFECT OF BAGASSE ASH ON MBD.....	37
TABLE 9	EFFECT OF BAGASSE ASH ON OMC.....	38
TABLE 10	EFFECT OF BAGASSE ASH ON 7 DAY UCS VALUE	39

LIST OF SYMOLS

Notation	Description
OMC	Optimum Moisture Content, in %
MDD	Maximum Dry Density, in g/cc
MBD	Maximum Bulk Density, in g/cc
UCS	Unconfined Compressive Strength, in MPa
FSI	Free Swell Index, in %
C_u	Coefficient of uniformity
C_c	Coefficient of curvature
BA	Bagasse Ash
Virgin Expansive Soil + x % Bagasse Ash	Mix of the Virgin Expansive Soil and x % Bagasse Ash by the dry weight of the soil.

CHAPTER 1

INTRODUCTION

1.1 General

For construction of any structure, it is duty of a responsible engineer to assess and evaluate the properties of the soil in order to know its geotechnical and engineering characteristics. After the evaluation, the properties can be modified suitably with various methods. In this work, an attempt has been made to modify the properties of expansive soil using industrial solid waste Bagasse Ash.

1.2 Expansive Soil

Expansive soils may be defined as the soils that expand in volume with the ingress of water and shrink when the soils get devoid of water. The variation of volume depends upon the moisture content, also many researchers have shown swelling and shrinkage follow two different mechanisms and generally shrinkage limit does not relate to the swelling characteristics of the soil. As a result of this volume change in soil, significant distress in the soil occurs, causing severe damage to the overlying structure. On the onset of the rainy season, these soils swell and lose their capacity to bear water and generally become softer. In the seasons which are relatively dry, these soils shrink due to evaporation of water and become harder. The resulting volume change can be the reason of cracking of the structures built upon it. The code of IS-1498 has given a basic idea about the classification of various expansive soil and their expansion characteristics based on their liquid limit and plasticity index values.

Expansive soils are problematic in nature and are generally encountered by geotechnical engineers in the process of designing structures like highways, retaining walls, buildings, backfills etc. Expansive soils are normally abundant in semi-arid regions. The cause may be due to the difference in evaporation and precipitation.

Various attempts at stabilization of expansive soil have been performed by a plethora of researchers using admixtures like lime, bitumen or cement. Although the stabilization with these admixtures is effective; it is not very much compatible from an economic view point. Attempts have been made to stabilize expansive soil with various locally available materials which are cheap and abundantly available in that very region where the problematic soil is present. Various wastes, whose disposal becomes a problem, are tried as admixtures to modify the property of soils.

1.3 Bagasse Ash

When it comes to sugar producing countries, India is ranked second in the production of sugar in the whole world. India has one-fifth of the total sugar industries of the world and accounts for almost one-seventh of the global production. In the process of sugar production, Bagasse is one of the major solid wastes produced. After the juice is extracted from the sugar cane, a fibrous matter remains which is generally termed as Bagasse. Indian sugar industries produce Bagasse up to an amount of 100MT per year. The deposition of Bagasse is uneven, random and is done in an unscientific manner which causes problems like valuable space reduction of the industrial area and other geo-environmental problems. If the solid waste is utilized in a proper manner to stabilize the expansive soil such problems can be avoided and the valuable space of the above said industry may be saved. When the Bagasse is burned Bagasse Ash is formed which is used in this particular study. The Bagasse ash is used as a replacement at various percentages; the properties of the virgin soil and the mixes are compared and the result is analyzed in a graphical manner to find out the major changes in the properties of soil.

CHAPTER 2

LITERATURE REVIEW

2.1 Previous Works

A limited number of studies have been done on the utilization of Bagasse Ash as an admixture to modify the properties of expansive soil. Few of the researches also include other waste materials along with the use of Bagasse Ash as admixtures to improve the properties of expansive soil.

Akshaya Kumar Sabat (2012) has investigated and reported that the addition of Bagasse Ash as an admixture to the expansive soil causes decrease in the MDD and causes increase in the value of OMC. The study has also reported that Bagasse Ash and lime sludge can be used for increasing the strength of flexible pavements in an economically suitable manner.

K. S. Gandhi (2012) has investigated the effects of Bagasse Ash on the properties of expansive soil and has reported a decrease in the value of plasticity index and free swell index of the expansive soil using Bagasse Ash in the proportions of 3 to 10%. The study has also shown that Bagasse Ash reduces the moisture content of wet soils in an effective manner and augments initial strength which is a necessary property for constructions in unstable and excessively moist ground conditions.

Moses, G and Osinubi, K. J. (2013) studied the impact of compactive effort on expansive soil samples which were treated with up to 8% Ordinary Portland cement (OPC) mixed with up to 8% Bagasse Ash (BA) by the dry weight of soil and were compacted by Standard Proctor (SP). The study reported an optimal blend of 8% OPC/ 4% BA as the suitable mixture.

Prakash Chavan and Dr.M.S.Nagakumar (2014) have reported the decreasing of plasticity index of expansive soil using Bagasse Ash. The study has also shown that up to an addition of 9% Bagasse Ash, MDD increases and OMC decreases. The study also has reported the increase in UCS values of the same soil at 9% Bagasse Ash content.

C. Rajakumar, T. Meenambal, and P. D. Arumairaj (2014) have reported the increasing of UCC strength with the addition of Coal ash + Bagasse ash, Coal Ash + Groundnut shell ash, and Bagasse ash + Groundnut shell ash with proportions which are uniform.

Amit S. Kharade, Vishal V. Suryavanshi, Bhikaji S. Gujar, and Rohankit R. Deshmukh (2014) have reported that at an effective replacement of 6% Bagasse Ash, the maximum dry density increased by 5.8% and have also suggested that the effective replacement of 6% Bagasse Ash is the optimum blend for an economic approach.

2.2 Properties of Soil

2.2.1 Specific Gravity

Specific Gravity may be termed as the ratio between the mass of any substance of a certain volume to the mass of the same volume of water. It basically tells us how heavier is the soil compared to water.

2.2.2 Particle Size Distribution

Soil is composed of particles of a plethora of shapes and sizes; the range of particle size of soil varies from microns to centimetres depending on various parameters like the place of origin soil, physical weathering and chemical weathering. The physical properties of soil like, density, permeability and strength are determined and affected fully or partially by the size and gradation

of particles present in the soil mass. There are various methods like, dry sieve analysis, wet sieve analysis and other methods to determine the particle size of the concerned soil sample. Generally the data is plotted on a graph paper, which is semi-log in nature and whose ordinate is the percentage finer and whose abscissa is the particle diameter which is defined by the sieve size. The abscissa is generally plotted on a logarithmic scale. The soil is termed as well graded if all the sizes of particle are abundant in a uniform manner. The soil is termed as poorly or uniformly graded if the particles of different size are available either excessively or are deficient.

2.2.3 Atterberg Limits

2.2.3.1 Liquid Limit

Liquid limit may be termed as that moisture content at which the soil behavior changes from plastic to liquid. Indian standard code has provided information regarding the measure of expansive soil relating to its liquid limit.

2.2.3.2 Plastic Limit

The difference between liquid limit and plastic limit is termed as the plasticity index and it is also a deciding factor for any construction.

2.2.3.3 Shrinkage Limit

It is that moisture content after which any moisture reduction in the soil does not cause any volume change.

2.2.4 Free Swell Index

The expansivity of the soil can also be predicted from the FSI value which is the differential increase in volume of soil when it comes under the influence of water or moisture content.

2.2.5 Unconfined Compression Test (UCS Test)

UCS or Unconfined Compression Test is just a specialized phenomenon of tri axial test in which the applied horizontal forces are zero. The sample is not confined horizontally and is only subjected to vertical loading until the failure occurs under shear.

Various samples are tested with different periods of curing to obtain and compare the strength of soil under the effect of various admixtures.

CHAPTER 3

EXPERIMENTAL INVESTIGATIONS

3.1 SCOPE OF WORK

The objective is to compare the various geotechnical properties of the Virgin Expansive Soil with the mixes of Virgin Expansive Soil and Bagasse Ash. To be specific, four types of mixes were prepared:

- Virgin Expansive Soil + 4% Bagasse Ash by dry weight of Soil
- Virgin Expansive Soil + 8% Bagasse Ash by dry weight of Soil
- Virgin Expansive Soil + 12% Bagasse Ash by dry weight of Soil
- Virgin Expansive Soil + 16% Bagasse Ash by dry weight of Soil

The experiments conducted in the laboratory are as follows:

1. Determination of specific gravity of the expansive soil.
2. Determination of Grain size distribution curve of expansive soil.
3. Determination of Maximum Dry Density (MDD) and Optimum Moisture

Content (OMC) of soil sample and different mixes of soil sample and Bagasse Ash by Standard Procter Test.

4. Determination of Liquid limit of soil sample and different mixes of soil sample and Bagasse Ash.
5. Determination of Plastic limit of soil sample and different mixes of soil sample and Bagasse Ash.
6. Determination of Shrinkage limit of soil sample and different mixes of soil sample and Bagasse Ash.

7. Determination of Free Swell Index of soil sample and different mixes of soil sample and Bagasse Ash.

8. Determination of Unconfined Compressive Strength by UCS Test of soil samples and different mixes of soil sample and Bagasse Ash. UCS Test is done because it is not always possible to perform bearing capacity test in field conditions. It is economically favourable to collect the undisturbed sample from the field and determine its strength in the laboratory. When it comes to choose a suitable material for the construction of embankment, it is comfortable to perform UCS Tests on both the undisturbed and remoulded sample. Shear strength can be found out by dividing the compressive strength by 2.

3.2 MATERIALS

Expansive soil: The expansive soil was collected from Nagpur, India. The sample was collected at a depth of 150 mm below the ground. Manual labour was employed to collect the sample. The soil was packed and transported to the place of study via train.

Bagasse: The Bagasse was collected from Bolangir, India. The Bagasse was collected from the field where the Bagasse Ash was dumped in layers. The Bagasse was collected and packed and brought to the place of study via roadways.

3.3 PREPARATION OF SAMPLES

Expansive Soil

The sample was first left out to dry in contact with direct sunlight and the clods present were broken to achieve uniformity of the sample. The sample was made devoid of small debris and other organic wastes. The sample was then oven-dried for 24 hours at 105 C.

The image of a sample of the expansive soil is given next.



FIGURE 1 SAMPLE OF THE EXPANSIVE SOIL

Bagasse Ash

The Bagasse collected was dried in the sun and the lumps were broken. The Bagasse was burnt in the Muffle Furnace at 600 degree Celsius for 24 hours to devoid it of any organic matter present and thus to prepare the Bagasse Ash. The Bagasse ash was then cooled for 6 hours and was mixed with expansive soil to form various mixes.

The image of a sample of the Bagasse Ash is given next.



FIGURE 2 SAMPLE OF THE BAGASSE ASH

CHAPTER 4

RESULTS

Different tests were done on Virgin Expansive Soil and various mixes described in section 3.1. The test results are arranged below in the order of replacement of percentage of Bagasse Ash by the dry weight of soil.

4.1 VIRGIN EXPANSIVE SOIL

4.1.1 Specific Gravity

The specific gravity of the Virgin Expansive Soil was found out to be 2.61.

4.1.2 Free Swelling Index

The free swelling index of the soil was found out to be 33.33%.

4.1.3 Grain size distribution

Dry sieve analysis was done with sieves of sizes

4.75mm

2mm

1mm

0.6mm

0.425mm

0.3mm

0.212mm

0.15mm

0.075mm

respectively.

After that sedimentation analysis was done with particles finer than 0.075 mm sieves. The hydrometer reading was taken at 12 time instances. The values obtained are plotted in the semi-log graph below. Where the y-axis represents the % finer and the x-axis represents particle size on a logarithmic scale.

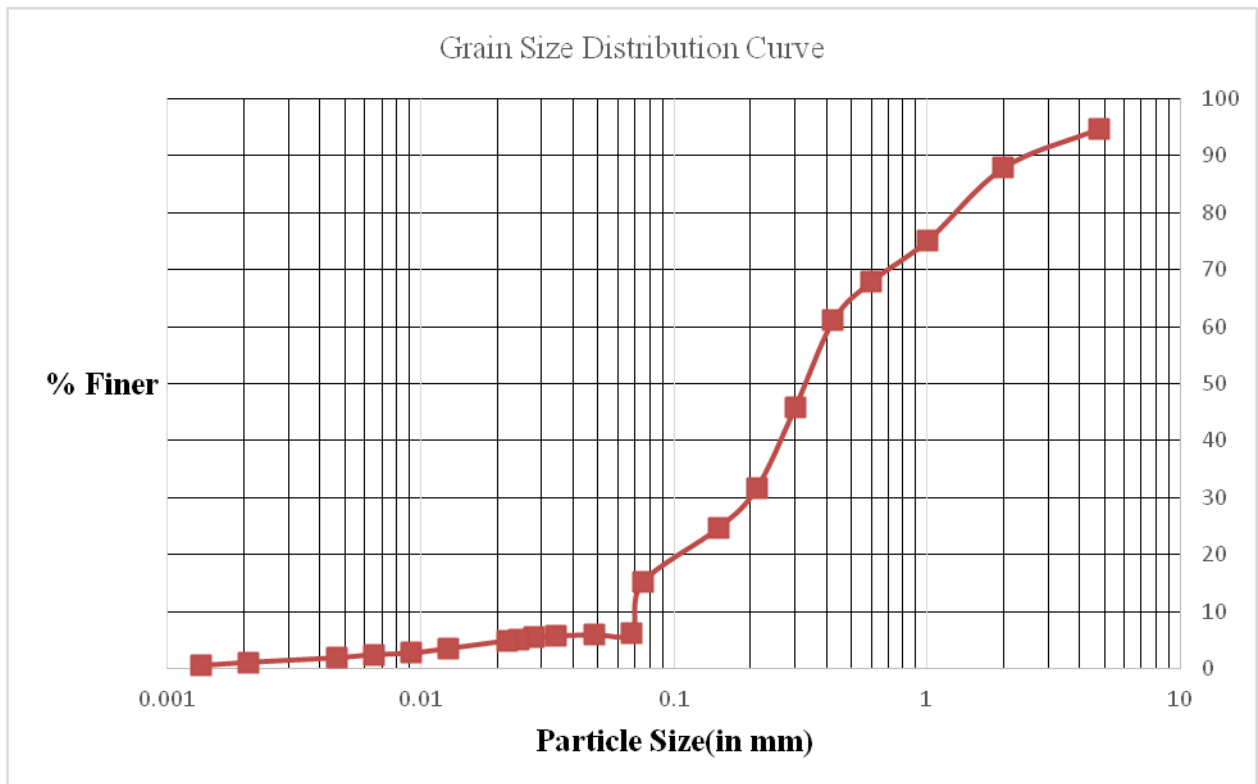


FIGURE 3 GRAIN SIZE DISTRIBUTION CURVE

The following data are obtained from the grain size distribution curve.

D_{60} = Soil particles finer than 60% of the total mass of the soil sample.

D_{60} = 0.416 mm

D_{30} = Soil particles finer than 30% of the total mass of the soil sample.

D_{30} = 0.197mm

D_{10} = Soil particles finer than 10% of the total mass of the soil sample.

D_{10} = 0.071mm

C_u = Coefficient of Uniformity = 5.86

C_c = Coefficient of Curvature = 1.314

4.1.4 Liquid Limit

The liquid limit of the Virgin Expansive Soil was found out to be 45.22%.

4.1.5 Plastic Limit

The plastic limit of the Virgin Expansive Soil was found out to be 27.17%.

4.1.6 Shrinkage Limit

The shrinkage limit of the Virgin Expansive Soil was found out to be 12.78%.

4.1.7 Standard Proctor Compaction Test

The maximum dry density was found out to be 1.78 g/cc. The optimum moisture content was found out to be 17.96%.

4.1.8 Unconfined Compressive Strength Test

The Unconfined Compressive Strength Test value of the Virgin Expansive Soil was found out to be:

7 DAY Unconfined Compressive Strength: 0.415 MPa.

4.2 VIRGIN EXPANSIVE SOIL + 4% BAGASSE ASH

4.2.1 Free Swelling Index

The free swelling index of the Virgin Expansive Soil + 4% Bagasse Ash was found out to be 26.67%.

4.2.2 Liquid Limit

The liquid limit of the Virgin Expansive Soil + 4% Bagasse Ash was found out to be 43.13%.

4.2.3 Plastic Limit

The plastic limit of the Virgin Expansive Soil + 4% Bagasse Ash was found out to be 27.85%.

4.2.4 Shrinkage Limit

The shrinkage limit of the Virgin Expansive Soil + 4% Bagasse Ash was found out to be 14.37%.

4.2.5 Standard Proctor Compaction Test

The maximum dry density was found out to be 1.73 g/cc. The optimum moisture content was found out to be 19.03%.

4.2.6 Unconfined Compressive Strength Test

The Unconfined Compressive Strength Test value of the Virgin Expansive Soil + 4% Bagasse Ash was found out to be:

7 DAY Unconfined Compressive Strength: 0.425 MPa.

4.3 VIRGIN EXPANSIVE SOIL + 8% BAGASSE ASH

4.3.1 Free Swelling Index

The free swelling index of the Virgin Expansive Soil + 8% Bagasse Ash was found out to be 30%.

4.3.2 Liquid Limit

The liquid limit of the Virgin Expansive Soil + 8% Bagasse Ash was found out to be 41.03%.

4.3.3 Plastic Limit

The plastic limit of the Virgin Expansive Soil + 8% Bagasse Ash was found out to be 28.61%.

4.3.4 Shrinkage Limit

The shrinkage limit of the Virgin Expansive Soil + 8% Bagasse Ash was found out to be 15.18%.

4.3.5 Standard Proctor Compaction Test

The maximum dry density was found out to be 1.63 g/cc. The optimum moisture content was found out to be 20.8%.

4.3.6 Unconfined Compressive Strength Test

The Unconfined Compressive Strength test value of the Virgin Expansive Soil + 8% Bagasse Ash was found out to be:

7 DAY Unconfined Compressive Strength: 0.461 MPa

4.4 VIRGIN EXPANSIVE SOIL + 12% BAGASSE ASH

4.4.1 Free Swelling Index

The free swelling index of the Virgin Expansive Soil + 12% Bagasse Ash was found out to be 30%.

4.4.2 Liquid Limit

The liquid limit of the Virgin Expansive Soil + 12% Bagasse Ash was found out to be 42.03%.

4.4.3 Plastic Limit

The plastic limit of the Virgin Expansive Soil + 12% Bagasse Ash was found out to be 28.97%.

4.4.4 Shrinkage Limit

The shrinkage limit of the Virgin Expansive Soil + 12% Bagasse Ash was found out to be 16.41%.

4.4.5 Standard Proctor Compaction Test

The maximum dry density was found out to be 1.57 g/cc. The optimum moisture content was found out to be 22.51%.

4.4.6 Unconfined Compressive Strength Test

The Unconfined Compressive Strength Test value of the Virgin Expansive Soil + 12% Bagasse Ash was found out to be:

7 DAY Unconfined Compressive Strength: 0.388 MPa

4.5 VIRGIN EXPANSIVE SOIL + 16% BAGASSE ASH

4.5.1 Free Swelling Index

The free swelling index of the Virgin Expansive Soil + 16% Bagasse Ash was found out to be 33.33%.

4.5.2 Liquid Limit

The liquid limit of the Virgin Expansive Soil + 16% Bagasse Ash was found out to be 41.65%.

4.5.3 Plastic Limit

The plastic limit of the Virgin Expansive Soil + 16% Bagasse Ash was found out to be 29.55%.

4.5.4 Shrinkage Limit

The shrinkage limit of the Virgin Expansive Soil + 16% Bagasse Ash was found out to be 13.38%.

4.5.5 Standard Proctor Compaction Test

The maximum dry density was found out to be 1.53g/cc. The optimum moisture content was found out to be 26.02%.

4.5.6 Unconfined Compressive Strength Test

The Unconfined Compressive Strength Test value of the Virgin Expansive Soil + 16% Bagasse Ash was found out to be:

7 DAY Unconfined Compressive Strength: 0.329 MPa

CHAPTER 5

COMPARISON AND DISCUSSION

5.1 COMPARISON

5.1.1 Comparison of Liquid Limit Values

The liquid limit of the Virgin Expansive Soil is determined. The Virgin Expansive Soil is mixed with 4%, 8%, 12%, and 16% of Bagasse Ash respectively. The liquid limit values of these mixes are determined and the values are compared in the table given below.

% OF BAGASSE ASH	LIQUID LIMIT (%)
0	45.22
4	43.13
8	41.03
12	42.03
16	41.65

TABLE 1 EFFECT OF BAGASSE ASH ON LIQUID LIMIT VALUE

The graph of the above table is plotted next. Where the x-axis represents the percentages of Bagasse Ash added to the virgin soil and the y-axis represents the liquid limit values of the respective mixes.

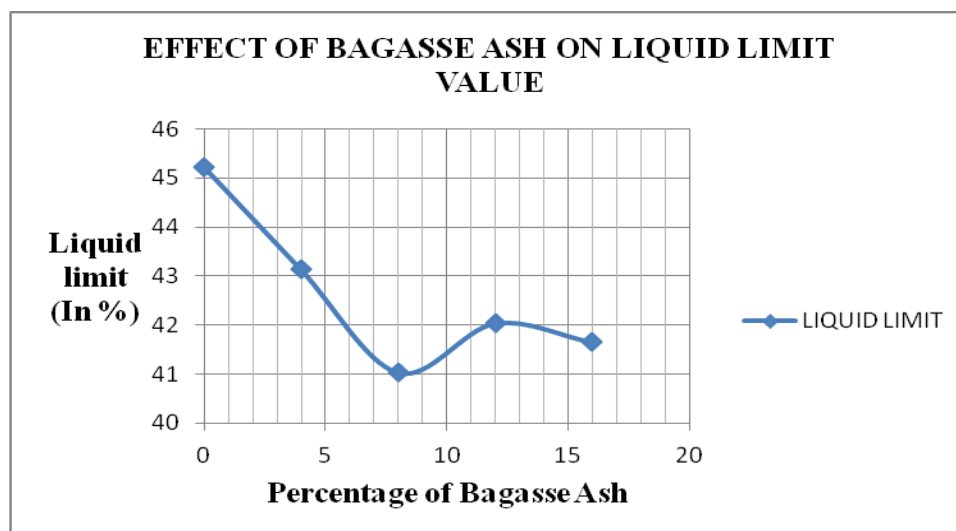


FIGURE 4 EFFECT OF BAGASSE ASH ON LIQUID LIMIT VALUE

5.1.2 Comparison of Plastic Limit Values

The plastic limit of the Virgin Expansive Soil is determined. The Virgin Expansive Soil is mixed with 4%, 8%, 12%, and 16% of Bagasse Ash respectively. The plastic limit values of these mixes are determined and the values are compared in the table given below.

% OF BAGASSE ASH	PLASTIC LIMIT (%)
0	27.17
4	27.85
8	28.61
12	28.97
16	29.55

TABLE 2 EFFECT OF BAGASSE ASH ON PLASTIC LIMIT VALUE

The graph of the above table is plotted below. Where the x-axis represents the percentages of Bagasse Ash added to the virgin soil and the y-axis represents the plastic limit values of the respective mixes.

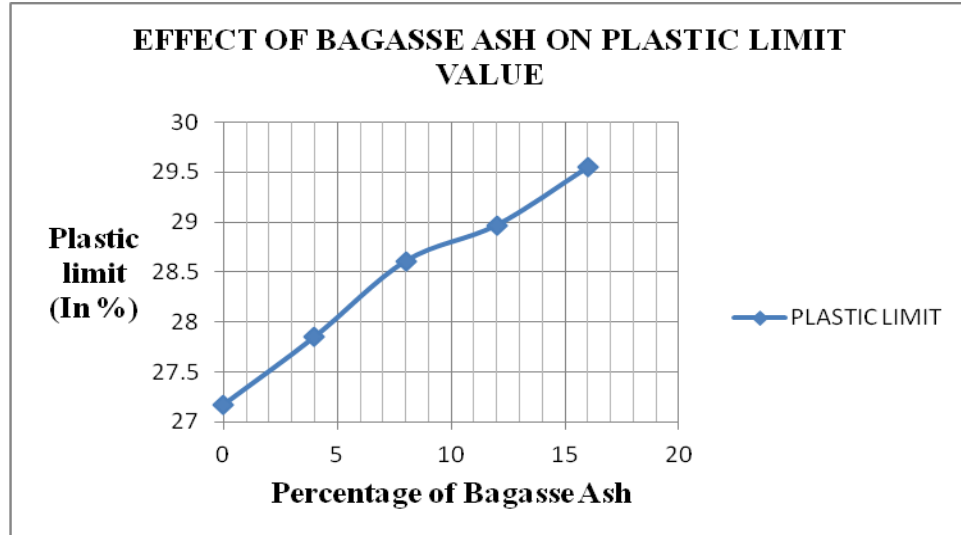


FIGURE 5 EFFECT OF BAGASSE ASH ON PLASTIC LIMIT VALUE

5.1.3 Comparison of Shrinkage Limit Values

The plastic limit of the Virgin Expansive Soil is determined. The Virgin Expansive Soil is mixed with 4%, 8%, 12%, and 16% of Bagasse Ash respectively. The plastic limit values of these mixes are determined and the values are compared in the table given next.

% OF BAGASSE ASH	SHRINKAGE LIMIT (%)
0	12.78
4	14.37
8	15.18
12	16.41
16	13.38

TABLE 3 EFFECT OF BAGASSE ASH ON SHRINKAGE LIMIT VALUE

The graph of the above table is plotted below. Where the x-axis represents the percentages of Bagasse Ash added to the virgin soil and the y-axis represents the shrinkage limit values of the respective mixes.

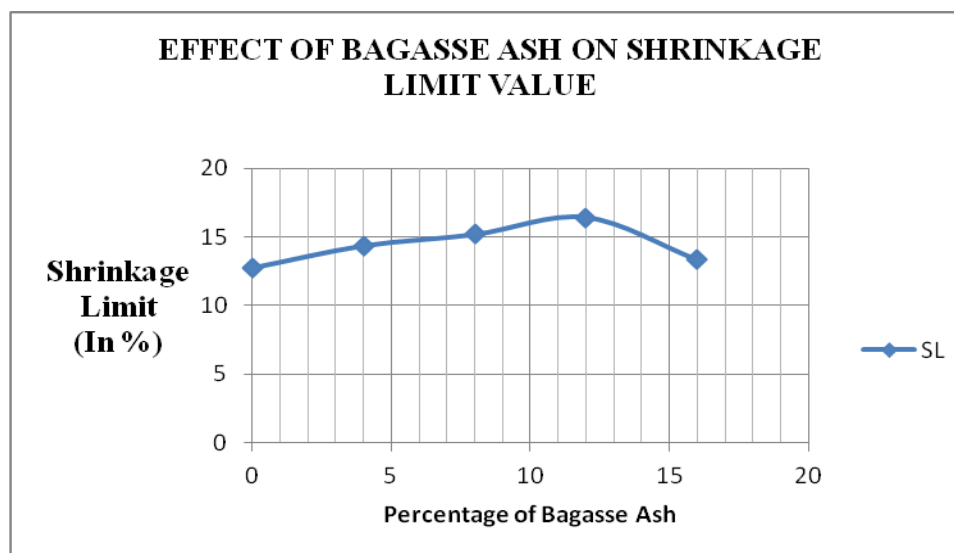


FIGURE 6 EFFECT OF BAGASSE ASH ON SHRINKAGE LIMIT VALUE

5.1.4 Comparison of Plastic and Liquid Limit Values

The liquid limit and plastic values are compared in the table below.

%OF BAGASSE ASH	LIQUID LIMIT (%)	PLASTIC LIMIT (%)
0	45.22	27.17
4	43.13	27.85
8	41.03	28.61
12	42.03	28.97
16	41.65	29.55

TABLE 4 COMPARISON OF LIQUID LIMIT AND PLASTIC LIMIT

The graph of the above table is plotted next. Where the x-axis represents the percentages of Bagasse Ash added to the virgin soil and the y-axis represents the liquid limit and plastic limit values of the respective mixes.

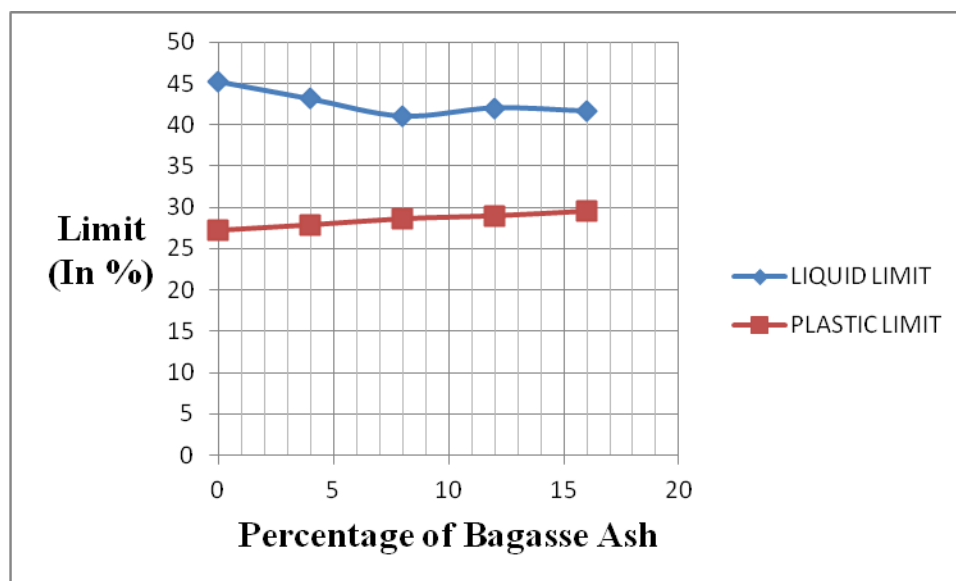


FIGURE 7 COMPARISON OF LIQUID LIMIT AND PLASTIC LIMIT

5.1.5 Comparison of Plasticity Index Values

The Plasticity Index of the Virgin Expansive Soil and the mixes are calculated. The values are compared in the table given below.

%OF BAGASSE ASH	PLASTICITY INDEX
0	18.05
4	15.28
8	12.42
12	13.06
16	12.1

TABLE 5 EFFECT OF BAGASSE ASH ON PLASTICITY INDEX

The graph of the above table is plotted next. Where the x-axis represents the percentages of Bagasse Ash added to the Virgin Expansive Soil and the y-axis represents the plasticity index values of the respective mixes.

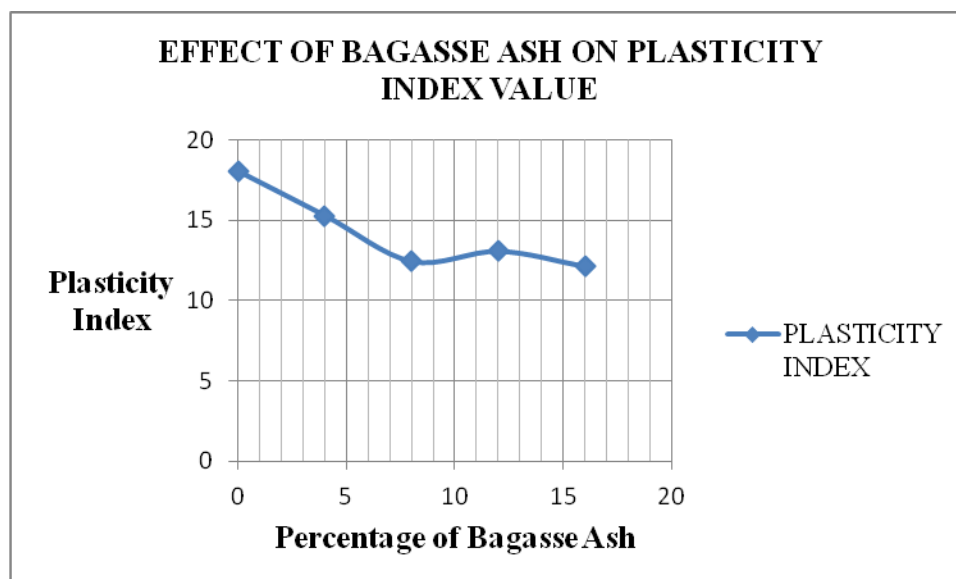


FIGURE 8 EFFECT OF BAGASSE ASH ON PLASTICITY INDEX VALUE

5.1.6 Comparison of Free Swell Index

The free swell index of the Virgin Expansive Soil and the mixes are determined. The values are compared in the table given next.

% OF BAGASSE ASH	FSI (%)
0	33.33
4	26.67
8	30.00
12	30.00
16	33.33

TABLE 6 EFFECT OF BAGASSE ASH ON THE FSI VALUE

The graph of the above table is plotted next. Where the x-axis represents the percentages of Bagasse Ash added to the virgin soil and the y-axis represents the Free Swell Index of the respective mixes.

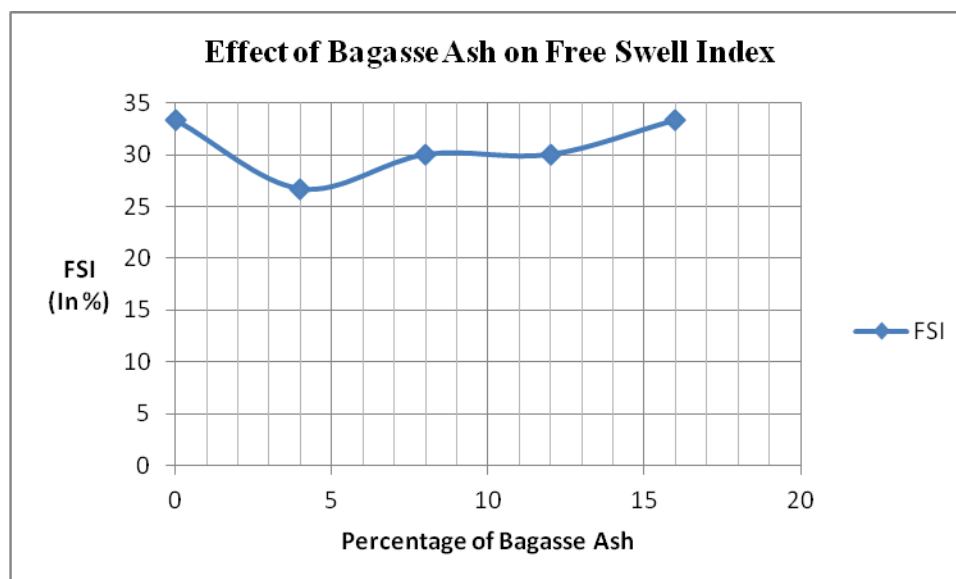


FIGURE 9 EFFECT OF BAGASSE ASH ON FREE SWELL INDEX

5.1.7 Comparison of Maximum Dry Density (MDD) Values

The Maximum Dry Density value of the Virgin Expansive Soil is determined. The Virgin Expansive Soil is mixed with 4%, 8%, 12%, and 16% of Bagasse Ash respectively. The Maximum Dry Density values of these mixes are determined and the values are compared in the table given below.

% OF BAGASSE ASH	MDD (g/cc)
0	1.78
4	1.73
8	1.64
12	1.57
16	1.53

TABLE 7 EFFECT OF BAGASSE ASH ON MDD

The graph of the above table is plotted below. Where the x-axis represents the percentages of Bagasse Ash added to the virgin soil and the y-axis represents the Maximum Dry Density values of the respective mixes.

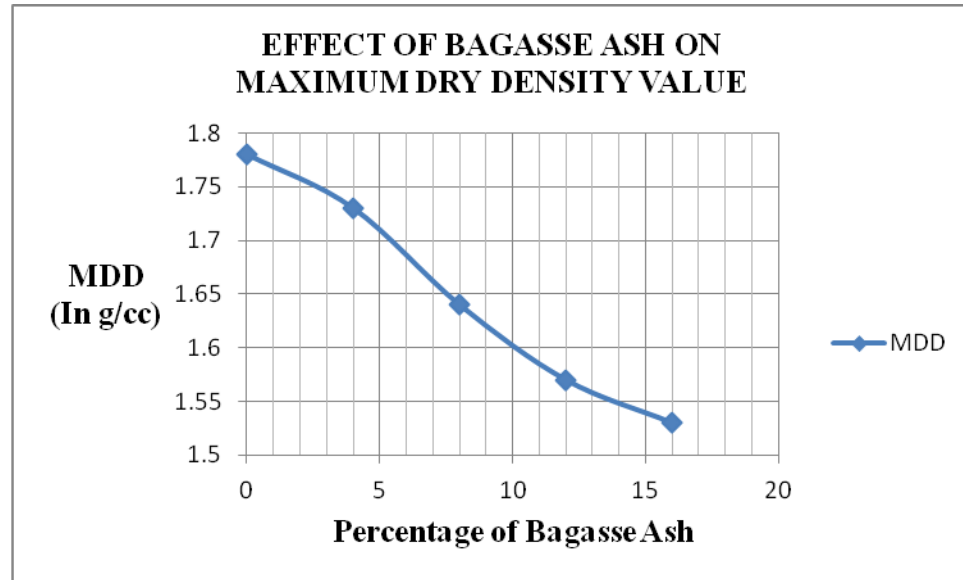


FIGURE 10 EFFECT OF BAGASSE ASH ON MAXIMUM DRY DENSITY VALUE

5.1.8 Comparison of Maximum Bulk Density (MBD) Values

The Maximum Bulk Density value of the Virgin Expansive Soil is determined. The Virgin Expansive Soil is mixed with 4%, 8%, 12%, and 16% of Bagasse Ash respectively. The Maximum Bulk Density values of these mixes are determined and the values are compared in the table given next.

% OF BAGASSE ASH	MBD (g/cc)
0	2.1
4	2.06
8	1.98
12	1.92
16	1.93

TABLE 8 EFFECT OF BAGASSE ASH ON MBD

The graph of the above table is plotted below. Where the x-axis represents the percentages of Bagasse Ash added to the virgin soil and the y-axis represents the Maximum Bulk Density values of the respective mixes.

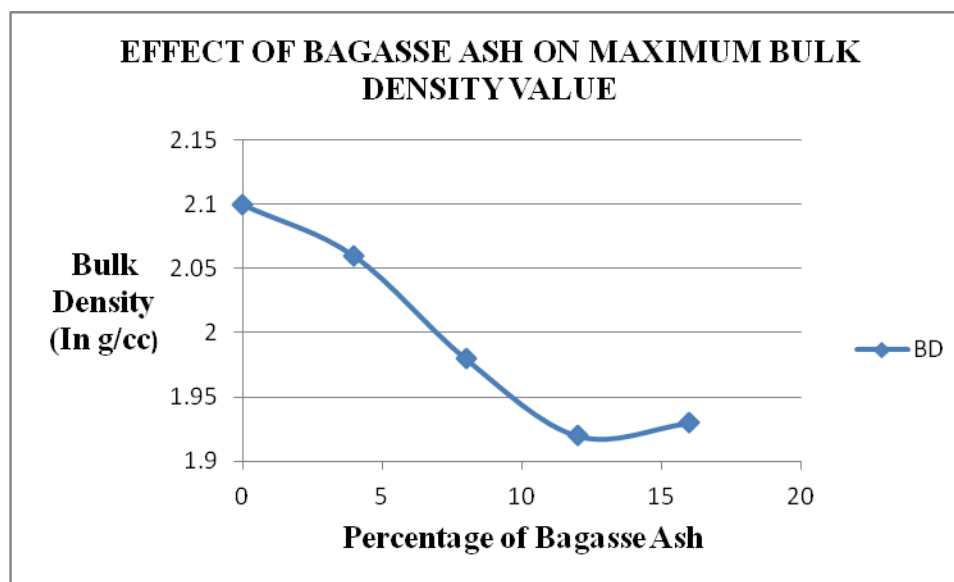


FIGURE 11 EFFECT OF BAGASSE ASH ON MAXIMUM BULK DENSITY VALUE

5.1.9 Comparison of Optimum Moisture Content (OMC) Values

The Optimum Moisture Content of the Virgin Expansive Soil is determined. The Virgin Expansive Soil is mixed with 4%, 8%, 12%, and 16% of Bagasse Ash respectively. The Optimum Moisture Content values of these mixes are determined and the values are compared in the table given below.

% OF BAGASSE ASH	OMC (%)
0	18
4	19
8	20.8
12	22.5
16	26

TABLE 9 EFFECT OF BAGASSE ASH ON OMC

The graph of the above table is plotted next. Where the x-axis represents the percentages of Bagasse Ash added to the virgin soil and the y-axis represents the Optimum Moisture Content of the respective mixes.

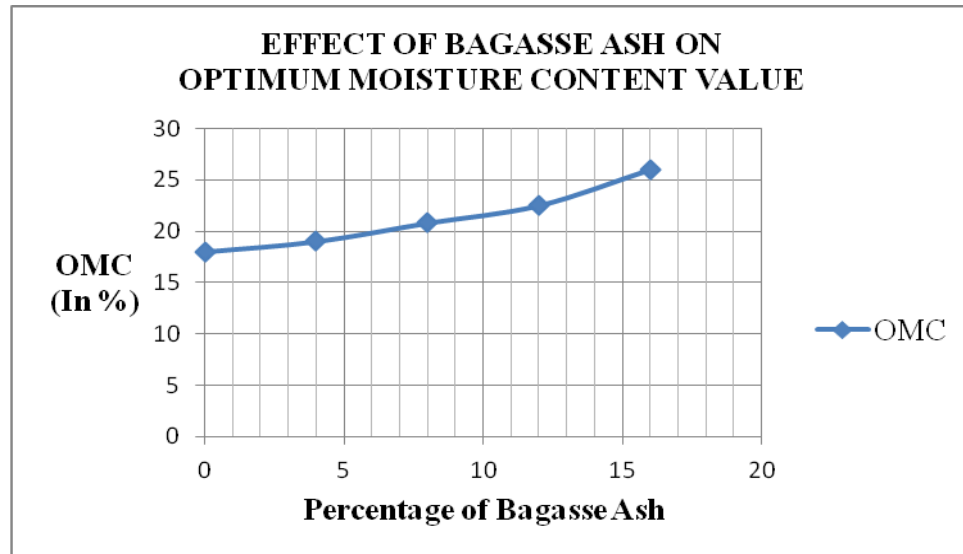


FIGURE 12 EFFECT OF BAGASSE ASH ON OPTIMUM MOISTURE CONTENT VALUE

5.1.10 Comparison of 7 Day UCS Values

The 7 Day UCS values are compared in the table given below.

% OF BAGASSE ASH	UCS VALUE (MPa)
0	0.415
4	0.425
8	0.461
12	0.388
16	0.329

TABLE 10 EFFECT OF BAGASSE ASH ON 7 DAY UCS VALUE

The graph of the above table is plotted below. Where the x-axis represents the percentages of Bagasse Ash added to the virgin soil and the y-axis represents the 7 Day UCS value of the respective mixes.

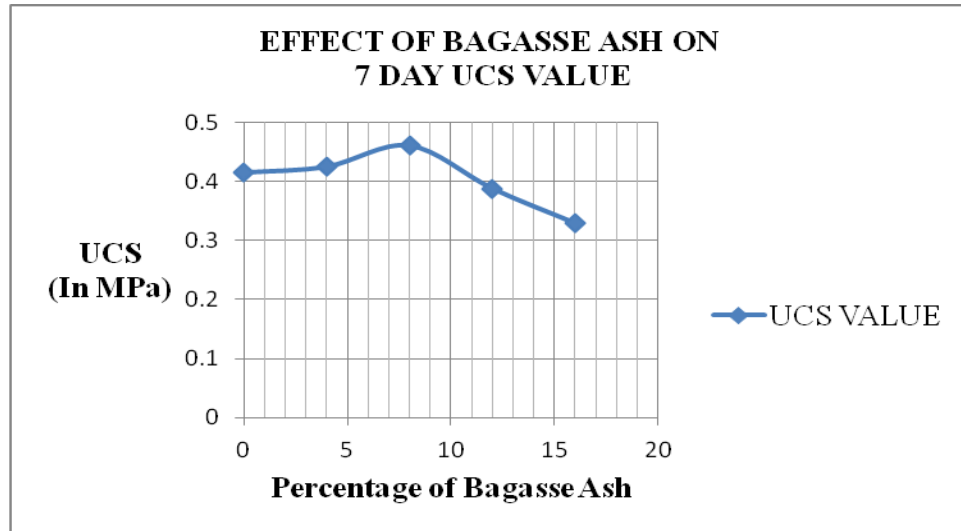


FIGURE 13 EFFECT OF BAGASSE ASH ON 7 DAY UCS VALUE

5.2 DISCUSSION

The Free Swell index of the soil is found to be decreasing up to the addition of 4% Bagasse Ash and is equal to the soil mix consisting of soil and 8% Bagasse Ash. The value increases at the addition of 12% Bagasse Ash, yet is less than that of virgin soil and the value increases at the addition of 16% Bagasse Ash and becomes equal to Free Swell Index of the Virgin Expansive Soil.

The liquid limit value decreases up to 8% addition of Bagasse Ash and increases up to 16% addition of Bagasse Ash. The liquid limit values at 12% and 16% addition of Bagasse Ash are less than that of Virgin Expansive Soil.

The plastic limit value increases up to 16% replacement of Bagasse Ash.

The shrinkage limit value increases up to 12% replacement of Bagasse and decreases at 16% replacement of Bagasse Ash.

The plasticity index decreases up to 8%, increases at 12% and decrease at 16% replacement of Bagasse Ash.

The MDD decreases constantly up to 16% replacement of Bagasse Ash.

The OMC decreases constantly up to 16% replacement of Bagasse Ash.

The MBD decreases constantly up to 12% replacement of Bagasse Ash and increases slightly at 16% replacement of Bagasse Ash.

The 7 Day UCS value increases up to 8% replacement of Bagasse Ash and decreases up to 16% replacements of Bagasse Ash.

CHAPTER 6

CONCLUSION

The addition of Bagasse Ash with Expansive Soil at various replacements, namely, 4%, 8%, 12% and 16% was studied for various changes in properties like, Atterberg limits, plasticity index and UCS values.

On the basis of the present study, the following conclusions were drawn.

- The addition of Bagasse Ash with the expansive soil reduced its plasticity and the minimum plasticity index was obtained at a replacement of 16% Bagasse Ash.
- The minimum liquid limit value was obtained at a replacement of 8% Bagasse Ash.
- The maximum plastic limit value was obtained at a replacement of 16% Bagasse Ash.
- The MDD value decreases with the addition of Bagasse Ash as replacement.
- The OMC value increases with the addition of Bagasse Ash as replacement.
- The UCS value was found to be increasing up to 8% replacement of Bagasse ash and was found to be decreasing after that.

On a broader sense of view, if the Bagasse Ash is used on expansive soils as a replacement; it can solve the various geo-environmental problems rising due to its deposition and can also save the valuable space of the sugar industry and the expansive soil can also be suitably modified.

REFERENCES

1. Gandhi, K. S. (2012): Expansive Soil Stabilization Using Bagasse Ash, International Journal of Engineering Research & Technology (IJERT), Vol.1, Issue 5.
2. Moses, G and Osinubi, K. J. (2013): Influence of Compactive Efforts on Cement-Bagasse Ash Treatment of Expansive Black Cotton Soil, World Academy of Science, Engineering and Technology, Vol. 7.
3. Sabat, A.K., Pati, S. (2014): A Review of Literature on Stabilization of Expansive Soil Using Solid Wastes, EJGE, Vol. 19 [2014], Bund. U.
4. Kharade, A. S., Suryavanshi, V. V., Gujar, B. S., Deshmukh, R. R. (2014): Waste product 'Bagasse Ash' from sugar industry can be used as stabilizing material for expansive soils, IJRET: International Journal of Research in Engineering and Technology, Volume: 03, Issue: 03.
5. C. Rajakumar, T. Meenambal, and P. D. Arumairaj (2014): California bearing ratio of expansive subgrade stabilized with waste materials, International Journal of Advanced Structures and Geotechnical Engineering ISSN 2319-5347, Vol. 03, No. 01.
6. Amit S. Kharade, Vishal V. Suryavanshi, Bhikaji S. Gujar, Rohankit R. Deshmukh (2014): Waste Product 'Bagasse Ash' From Sugar Industry can be used as Stabilizing Material for Expansive Soils, IJRET: International Journal of Research in Engineering and Technology eISSN: 2319-1163 | pISSN: 2321-7308 Volume: 03 Issue: 03.
7. Prakash Chavan and Dr.M.S.Nagakumar (2014): STUDIES ON SOIL STABILIZATION BY USING BAGASSE ASH, International Journal of Scientific Research Engineering & Technology (IJSRET) ISSN: 2278-0882.